

Star-Like Micelles with Star-Like Interactions: A quantitative Evaluation of Structure Factors and Phase Diagram

M. Laurati, J. Stellbrink, R. Lund, L. Willner, and D. Richter
Institut für Festkörperforschung, Forschungszentrum Jülich
52425 Jülich, Germany

E. Zaccarelli

Dipartimento di Fisica and INFN-CRS SOFT, Università di Roma La Sapienza, P.zza A. Moro 2, I-00185, Roma, Italy
(Dated: February 2, 2008)

PEP-PEO block copolymer micelles offer the possibility to investigate phase behaviour and interactions of star polymers (ultra-soft colloids). A star-like architecture is achieved by an extremely asymmetric block ratio (1:20). Micellar functionality f can be smoothly varied by changing solvent composition (interfacial tension). Structure factors obtained by SANS can be quantitatively described in terms of an effective potential developed for star polymers. The experimental phase diagram reproduces to a high level of accuracy the predicted liquid/solid transition. Whereas for intermediate f a bcc phase is observed, for high f the formation of a fcc phase is preempted by glass formation.

PACS numbers: 61.12.Ex, 61.25.Hq, 64.70.Nd, 82.35.Jk

Star polymers, *i.e.* f polymer chains tethered to a central microscopic core, can be regarded as ultra-soft colloids bridging the properties of linear polymer chains and hard sphere colloids [1]. The hybrid character is reflected in their effective interaction potential introduced by Likos et al. [2],

$$\begin{aligned}\beta V(r) &= \frac{5}{18} f^{3/2} \left[-\ln\left(\frac{r}{\sigma}\right) + \frac{1}{1 + \sqrt{f}/2} \right], & r \leq \sigma \\ &= \frac{5}{18} f^{3/2} \frac{\sigma/r}{1 + \sqrt{f}/2} \exp \left[-\frac{\sqrt{f}(r - \sigma)}{2\sigma} \right], & r \geq \sigma\end{aligned}\quad (1)$$

with $\beta = 1/k_B T$, r the distance between star centers and σ the corona diameter. Eq. 1 has given good results in modelling small angle neutron scattering (SANS) data of star polymer solutions [2, 3]. The corresponding theoretical phase diagram [4] shows unique features, such as different crystalline phases depending sensitively on volume fraction ϕ and f . Recently the phase diagram has been revisited to include the glass transition as a result of dynamical arrest of the system [5], corroborating several experimental studies [3, 6, 7].

Unfortunately, the high interest in star polymers is not reflected in their availability. Synthesis requires considerable preparative efforts, therefore it is of particular interest to substitute star polymers by an easy to establish model system. Ideally, this analogue should not only show the typical molecular architecture of star polymers, but also interact via the effective potential given in Eq. 1.

A few attempts to connect micellar systems to star polymers have been done, however, approaching the star-like regime [8, 9] defined by the block ratio $N_a/N_b \gg 1$ (with a/b the soluble/insoluble block) is not trivial. Gast et al. investigated poly(styrene)-poly(isoprene) (PS-PI) block copolymers [10]. They found experimental

evidence for fcc and bcc phase formation, with crystalline geometry determined by block composition ($0.8 \leq N_a/N_b \leq 4$). Recently PS-PI [11] and PEO-PBO [12] micelles showed a temperature induced fcc-bcc transition. This transition could be related to changes in f and compared to the phase diagram of star polymers indicating some similarities in the interactions although the block ratio was rather small, $N_a/N_b \approx 2$ [11]. Micelles formed by hydrophobically modified PEO with $N_a/N_b \approx 150$ have been investigated [13], but interactions were characterized by mapping onto an equivalent hard sphere system. Therefore, a systematic study to correlate the star-like architecture of the individual micelle with star-like interactions has never been performed.

In this Letter we show that structure factors of poly(ethylene-alt-propylene)-poly(ethylene oxide) (PEP-PEO) micelles (which fulfill all prerequisites of the star-like regime [14, 15, 16]) provide the basis to investigate such a correlation. SANS measurements at core contrast allow a direct determination of experimental structure factors $S(Q)$ which can be described starting from Eq. 1 with parameters ϕ , f , and σ directly given by experimental values. In addition, we can reproduce to a high level of accuracy the liquid-solid transition of the theoretical phase diagram. This was done over a wide range of f and spanning the range from dilute to concentrated solutions, providing a comprehensive characterization of block copolymer micelles in terms of the microscopic, effective potential originally developed for star polymers.

The micellization behavior of PEP-PEO in aqueous solution is governed by the high interfacial tension, $\gamma=46$ mN/m, between PEP and water and shows the following features [14, 17]: i.) PEP-PEO forms micelles with the hydrophobic PEP constituting the core and the hydrophilic PEO constituting the corona. ii.) Micelles are even formed in a very asymmetric block composition with high PEO content ($N_a/N_b \approx 20$). iii.) All micellar

	M_n	M_w/M_n^a	D_p	x_h	$\rho[10^{10}cm^{-2}]$
PEP (block)	1100	1.06	15	1.0	-0.31
PEO (block)	20700	1.04	436	0.11	6.32
x_{DMF}	$\rho_0[10^{10}cm^{-2}]$	f^b	$R_{g,core}^b[\text{\AA}]$	$R_g^b[\text{\AA}]$	$R_g^c[\text{\AA}]$
0.0	6.33	136	31	194	192
0.1	6.32	94	29.5	179	161
0.2	6.34	82	29	164	154
0.3	6.33	73	27	150	140
0.4	6.31	67	27	140	136
0.5	6.31	63	26	135	127

^aoverall polydispersity by SEC

^bFrom form factor analysis

^cFrom $\bar{\sigma}$ values obtained from fits

TABLE I: Characterization of PEP-PEO block copolymer and micelles. D_p is the degree of polymerization, x_h the protonation fraction and ρ and ρ_0 the scattering length densities of polymer blocks and solvent. x_{DMF} is the molar fraction of DMF in the solvent, $R_{g,core}$ and R_g the core and overall micellar radius of gyration.

cores are completely segregated, *i.e.* not swollen by solvent. iv.) The micelles are kinetically frozen: Although chemically not linked, exchange of block copolymers between different micelles could not be observed, even not at elevated temperatures [18]. This means that no free chains, *i.e.* no depletion effects [19] are present in contrary to ref. [11]. v.) Adjusting γ by addition of a PEO selective cosolvent like N,N-dimethylformamide (DMF), allows to smoothly vary f even in the star-like regime (where $f \sim \gamma^{6/5}$ was confirmed by experiments [15]).

The asymmetric PEP-PEO block copolymer under study was synthesized by anionic polymerization [17]. To exploit h/d-contrast variation in our SANS experiments, the individual blocks have been selectively protonated/deuterated, see Tab. I. Using water/DMF mixtures we prepared samples with six different f going from dilute to the very concentrated regime. Since the micelles are kinetically frozen, all samples were directly prepared in the corresponding solvent mixture and annealed for at least 1 week, for experimental details see [15]. SANS data were corrected following standard procedures and normalized to absolute units to allow a quantitative theoretical interpretation.

The macroscopic scattering cross section, $(d\Sigma/d\Omega)(Q)$, measured by SANS can be expressed as a product of single particle contributions, the particle form factor $P(Q)$, and the structure factor $S(Q)$, which contains all information about particle interactions:

$$\left(\frac{d\Sigma}{d\Omega}\right)(Q) = N_z P(Q) S(Q) \quad (2)$$

Here N_z is the number density of particles. Experimental $S(Q)$ can be extracted from SANS data by dividing out the experimental $P(Q)$ measured in dilute solution. However, this procedure is only valid, if particle size and shape, *i.e.* $P(Q)$, are unaffected by concentration. This is in general not the case for deformable particles like

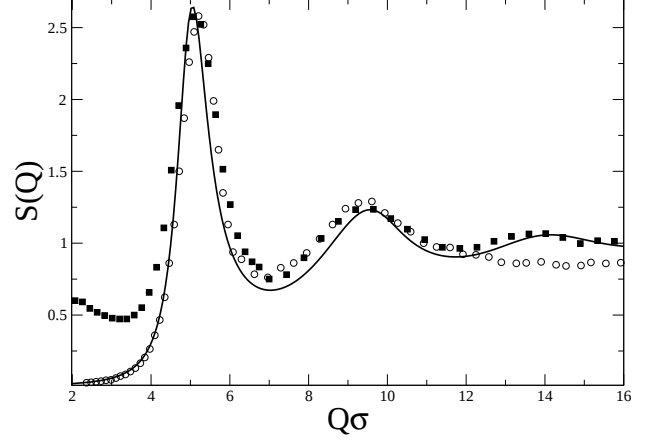


FIG. 1: $S(Q)$ for PEP-PEO micelles with $f = 63$ (■) compared to 64-arm (nominal) PB star (○), both samples have the same ratio $\phi/\phi^* \approx 1$. Solid line: Theoretical $S(Q)$ calculated by applying the RY-closure for the OZ-equation starting from Eq. 1, see text.

micelles, but we can overcome this problem by proper application of contrast variation techniques. Performing all SANS experiments in core contrast, *i.e.* adjusting the scattering length density ρ_0 of the solvent by use of h/d-isotopic mixtures to that of PEO, reduces the contrast factor between corona and solvent to zero, see Tab. I. Only the compact PEP core, which is completely unaffected by increasing concentration, is “visible” in the SANS experiment.

Micellar characteristics, *i.e.* functionality f , core radius R_c and overall micellar radius R_m have been determined as described in [15, 16]. R_g^b in Tab. I is calculated according to $R_g^b = \sqrt{5/11}R_m$ valid for star polymers, $R_{g,core}$ according to $R_{g,core} = \sqrt{3/5}R_c$ valid for solid spheres.

In this Letter we will focus on the results obtained from concentrated solutions, where particle interactions are dominant. Fig. 1 shows the comparison between $S(Q)$ obtained for micelles with $f = 63$ (water/DMF mixture with molar fraction $x_{DMF} = 0.5$) and a corresponding poly(butadiene) (PB) star polymer in methylcyclohexane with (nominal) 64 arms [3]. Both samples have been measured at a volume fraction $\phi \approx \phi^*$, with $\phi^* = 3/(4\pi R_m^3) \times (fM_w/\bar{d}N_A)$ being the overlap volume fraction and $\bar{d}$ the average density. All main features of the star $S(Q)$ with respect to peak positions and heights are perfectly reproduced. The only difference is found in the low Q region. Here the micellar $S(Q)$ shows some increase possibly indicating the presence of large scale structures in the micellar solution. These clusters might arise either from i.) (inherent) mesoscopic heterogeneities as also found for purely repulsive star polymer solutions [7, 20] or ii.) from weak attractive interactions due to the decreasing solvent quality with increas-

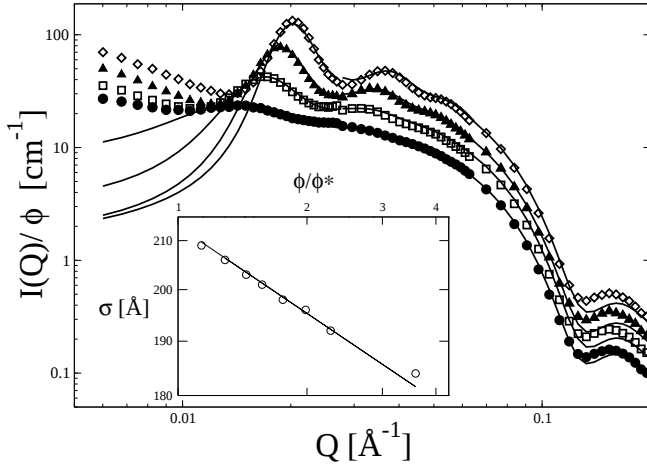


FIG. 2: Experimental intensities $I(Q)$ for $f = 63$ at different ϕ in the fluid phase, $\phi < \phi^*$: ($\bullet$) $\phi=0.017$, ($\square$) $\phi=0.034$, ($\blacktriangle$) $\phi=0.051$, ($\diamond$) $\phi=0.067$ and fits (solid lines). For clarity $I(Q)$ are divided by factors: ($\diamond$) 1, ($\blacktriangle$) 1.5, ($\square$) 2, ($\bullet$) 3. Inset: volume fraction dependence of σ for $f = 63$, showing the expected scaling behavior $\sigma \sim \phi^{-1/8}$ for $\phi > \phi^*$.

ing x_{DMF} [15]. At the moment the physical origin of clustering is not clear, but for case i.) this would only further support the analogy between PEP-PEO micelles and star polymers, and for case ii.) recent theoretical results have shown that weak attractive interactions do not substantially influence the features in the region of the main structure factor peak [21]. As will be shown below on the basis of our analysis, the low- Q scattering does not have major relevance on the quantitative interpretation of $S(Q)$ for $Q \geq 10^{-2} \text{Å}^{-1}$.

Fig. 1 also shows a fit to the experimental data using Eq. 1, with the corona diameter σ being the only adjustable parameter. The theoretical $S(Q)$ was calculated by applying the self-consistent Rogers-Young (RY) closure for the Ornstein-Zernike equation. This closure has already been proven to be quite accurate compared to simulations of the same model potential for relatively small f [21, 22]. Different $S(Q)$ have been calculated for a fine grid of functionalities around the experimental $f = 63$ to take into account the error on f . The experimental uncertainty on f is such that no significant changes in $S(Q)$ are observed. From this fit we found a corona diameter $\sigma = 226 \text{Å}$. The radius of gyration R_g can be calculated by $R_g = \sigma/2 + \sigma/\sqrt{f}$ [2]. The obtained $R_g = 127 \pm 7 \text{Å}$ from the fit is in very good agreement with $R_g = 135 \pm 10 \text{Å}$ found from independent SANS measurements of the micellar form factor [15]. Data analysis was further refined by directly fitting $(d\Sigma/d\Omega)(Q)$ including the convolution to the experimental resolution function [23]. We assumed a compact core model for $P(Q)$, fixing the parameters to f and R_c values obtained from the characterization of the micelles. The validity of this assumption can be rationalized from Fig. 2, where the minimum arising from the solid core appears at $Q \approx 0.13 \text{Å}^{-1}$ independent of ϕ .

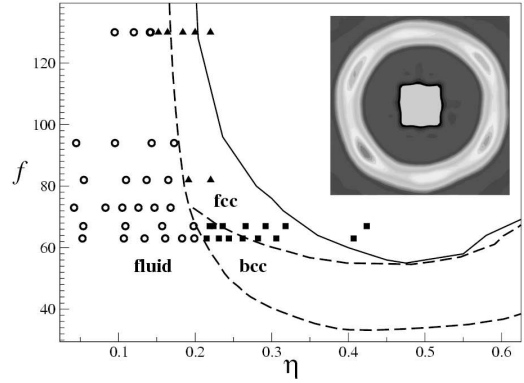


FIG. 3: Experimental phase diagram (symbols) of star-like micelles vs. theoretical phase diagram (lines) of star polymers. ($\circ$) liquid, ($\blacksquare$) bcc crystal and ($\blacktriangle$) gels. Dashed line represent equilibrium phase diagram from Ref.[2]. The solid line is the RY-ideal MCT glass line from Ref.[5]. Inset: 2-dimensional SANS detector picture of $f = 63$, $\phi=0.16$ evidencing Bragg reflections.

On the basis of the good agreement between theory and experiment we then applied this analysis procedure to all f and ϕ studied. The excellent quality of the fits for $Q \geq 10^{-2} \text{Å}^{-1}$ is shown in Fig. 2 for samples of different ϕ but same functionality $f = 63$. For $\phi \leq \phi^*$ we found a nearly constant corona diameter giving a mean value $\bar{\sigma} = 226 \pm 4$, which corresponds to the low concentration, unperturbed corona diameter. $\bar{\sigma}$ was then used to transform the given experimental number density N_z to the packing fraction $\eta = N_z \pi/6 \sigma^3$. R_g values calculated from $\bar{\sigma}$ are compared to results from form factor analysis in Tab. I.

Above ϕ^* we had to use a different approach for recalculating η . According to the Daoud-Cotton theory [24] the stars are expected to shrink as $\propto \phi^{-1/8}$, and indeed, the fit values for $\sigma(\phi \geq \phi^*)$ show exactly this scaling behaviour as shown in the inset of Fig. 2. Therefore we decided to use the individual $\sigma(\phi)$ for recalculating η . Calculating η this way for all f , we could then compare experimental and theoretical phase diagrams, as shown in Fig. 3. The transition from the liquid to the crystalline state (body centered cubic, bcc) predicted by theory is perfectly reproduced in experiments for $f = 63$ and $f = 67$. The experimental critical packing fraction for crystallization is found to be $\eta \approx 0.21$. Direct evidence for crystal formation comes from the presence of Bragg peaks in the 2-dimensional SANS pattern as shown in the inset of Fig. 3 for $f = 63$ and $\phi = 0.16$. Moreover crossing ϕ^* the first peak of $S(Q)$ assumes a value bigger than 2.8, which is the minimum value for a freezing transition according to the *Hansen-Verlet* criterion [25] (see Fig 4). The peak is further growing with increasing ϕ . Additionally for $\phi > \phi^*$ a third small peak is forming, and the position ratio between the three peaks is $1:\sqrt{2}:\sqrt{3}$ corresponding to a simple cubic (sc) or bcc lattice. The A15 lattice can be directly excluded, since its additional third reflection at $\sqrt{5}/2$ is expected to occur in a region

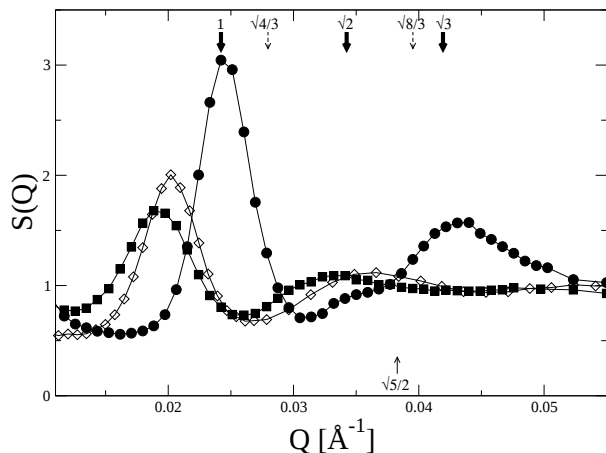


FIG. 4: Experimental $S(Q)$ for: ($\square$) $f = 130$, ($\diamond$) $f = 82$ and ($\circ$) $f = 67$ at $\eta \approx 0.22$, showing the crossover from gel to crystal with decreasing f . $S(Q)$ for $f = 67$ shows peak position ratios characteristic for bcc crystal (bold arrows). Expected peak positions for fcc (dashed arrows) and A15 crystals. Solid lines: Guide to the eye.

where the form factor is close to unity. A comparison of the lattice constants $a_{sc} = 270\text{\AA}$ and $a_{bcc} = 381\text{\AA}$ with $2R_m = 377\text{\AA}$ at Φ^* excludes the sc lattice, identifying the crystal as a bcc lattice. With increasing η no evidence for the predicted transition to a fcc phase is found in our data. However, we also note that for regular star polymers a bcc-fcc transition was never observed, probably due to the small free energy difference, $\approx kT$, between the two crystalline phases [26].

With increasing f the experimentally observed liquid-solid transition is in nearly perfect agreement with the phase boundary predicted by theory, but instead of observing a fcc phase we observe disordered solid-like structures for all $f \geq 73$. Location of the solidus line comes from a double evidence: First from tube inversion, which means that we tested the non-flowing behavior of the sample inverting sample holders in a bath at constant temperature. In addition, preliminary rheology exper-

iments confirm a non-zero storage modulus. Structure factor peaks for $\phi > \phi^*$ are definitely smaller than 2.8, excluding formation of a crystal, as shown in Fig. 4. Therefore we identify this disordered phase as a glass. The suppression of the expected equilibrium fcc phase and the early onset of glass formation at packing fractions smaller than expected from theory, might arise from an "effective" polydispersity induced by the clusters discussed above [27]. At lower f , where MCT glass line and crystal line are well separated, this effect does not play such an important role and we do observe the crystal there

In conclusion, we have shown that star-like PEP-PEO micelles show the same interactions as star polymers, giving a significant experimental support to the picture of star polymers as ultra-soft colloids. We have been able to quantitatively describe experimental structure factors $S(Q)$ starting from a microscopic effective potential predicted for star polymers. The softness of the interaction potential between star-like micelles can be precisely varied by adjusting the interfacial tension γ between PEP and the used solvent. In addition, we performed a detailed investigation of the phase diagram as a function of functionality f and packing fraction. In particular we determined the critical packing fraction for liquid-bcc crystal transition, finding excellent agreement with theory. The simple synthesis of PEP-PEO block copolymers compared to star polymers in combination with the shown analogy in terms of effective interactions establish these micelles an excellent alternative for investigating the phase behaviour of ultra-soft colloids.

We acknowledge the allocation of SANS beam time by FZJ, ILL and LLB and assistance during the SANS experiments by A. Radulescu (FZJ), P. Lindner (ILL), and L. Noirez (LLB). We acknowledge helpful discussions with C.N. Likos. This work was supported by the Deutsche Forschungsgemeinschaft in the framework of the Transregio-SFB TR6. E. Zaccarelli acknowledges support from MIUR Cofin 2002 and FIRB.

-
- [1] G. Grest, L. Fetters, J. Huang, and D. Richter, *Adv. Chem. Phys.* **94**, 67 (1996).
 - [2] C. Likos, H. Löwen, M. Watzlawek, B. Abbas, O. Jucknische, J. Allgaier, and D. Richter, *Phys. Rev. Lett.* **80**, 4450 (1998).
 - [3] J. Stellbrink, J. Allgaier, M. Monkenbusch, D. Richter, A. Lang, C. Likos, M. Watzlawek, H. Löwen, G. Ehlers, and P. Schleger, *Prog. Colloid Polym. Sci.* **115**, 88 (2000).
 - [4] M. Watzlawek, C. Likos, and H. Löwen, *Phys. Rev. Lett.* **82**, 5289 (1999).
 - [5] G. Foffi, F. Sciortino, P. Tartaglia, E. Zaccarelli, F. L. Verso, L. Reatto, K. Dawson, and C. Likos, *Phys. Rev. Lett.* **90**, 5289 (2003).
 - [6] D. Vlassopoulos, G. Fytas, T. Pakula, and J. Roovers, *J. Phys: Condens. Matter* **13**, R855 (2001).
 - [7] M. Kapnistos, D. Vlassopoulos, G. Fytas, K. Mortensen, G. Fleischer, and J. Roovers, *Phys. Rev. Lett.* **85**, 4072 (2000).
 - [8] I. Hamley, *The Physics of Block Copolymers* (Oxford University Press, 1998).
 - [9] A. Halperin, M. Tirrell, and T. Lodge, *Adv. Polym. Sci.* **100**, 31 (1992).
 - [10] G. McConnell, A. Gast, J. Huang, and S. Smith, *Phys. Rev. Lett.* **71**, 2102 (1993).
 - [11] T. Lodge, J. Bang, M. Park, and K. Char, *Phys. Rev. Lett.* **92**, 145501 (2004).
 - [12] I. Hamley, J. Pople, and O. Diat, *Colloid Polym. Sci.* **276**, 446 (1998).
 - [13] E. Beaudoin, O. Borisov, A. Lapp, L. Billon, R. Hiorns,

- and J. Francois, *Macromolecules* **35**, 7436 (2002).
- [14] L. Willner, A. Poppe, J. Allgaier, J. Monkenbusch, P. Lindner, and D. Richter, *Europhys. Lett.* **51**, 628 (2000).
 - [15] R. Lund, L. Willner, J. Stellbrink, A. Radulescu, and D. Richter, *Macromolecules* **37**, 9984 (2004).
 - [16] J. Stellbrink, G. Rother, M. Laurati, R. Lund, L. Willner, and D. Richter, *J. Phys.: Condens. Matter* **16**, S3821 (2004).
 - [17] A. Poppe, L. Willner, J. Allgaier, J. Stellbrink, and D. Richter, *Macromolecules* **30**, 7462 (1997).
 - [18] R. Lund, Ph.D. thesis, Universität Münster (2004).
 - [19] E. Stiakakis, D. Vlassopoulos, C. Likos, J. Roovers, and G. Meier, *Phys. Rev. Lett.* **89**, 208302 (2002).
 - [20] J. Stellbrink, J. Allgaier, and D. Richter, *Phys. Rev. E* **56**, R3772 (1997).
 - [21] F. L. Verso, M. Tau, and L. Reatto, *J. Phys.: Condens. Matter* **15**, 1505 (2003).
 - [22] M. Watzlawek, H. Löwen, and C. Likos, *J. Phys.: Condens. Matter* **10**, 8189 (1998).
 - [23] J. Pedersen, D. Posselt, and K. Mortensen, *J. Appl. Cryst.* **23**, 321 (1990).
 - [24] M. Daoud and J. Cotton, *J. Phys. (Paris)* **43**, 531 (1982).
 - [25] J. Hansen and L. Verlet, *Phys. Rev.* **184**, 151 (1969).
 - [26] M. Watzlawek, Ph.D. thesis, University of Dusseldorf (1999).
 - [27] F. Sciortino, S. Mossa, E. Zaccarelli, and P. Tartaglia, *Phys. Rev. Lett.* **93**, 055701 (2004).